

Polymer and Colloid Highlights

Division of Polymers, Colloids and Interfaces

A Division of the Swiss Chemical Society

Metalocene as Mechanophore in Polymers Leads to Metal Ion Release & Oxidation

Michela Di Giannantonio, Mathieu A. Ayer, Ester Verde-Sesto, Marco Lattuada, Christoph Weder, and Katharina M. Fromm*

*Correspondence: Prof. K. M. Fromm, Department of Chemistry, University of Fribourg, Switzerland. E-mail: katharina.fromm@unifr.ch

Keywords: Mechanochemistry · Organometallic chemistry · Polymers · Stimuli-Responsive Polymers · Ultrasound

Stimuli-responsive polymers are high-performance materials that can change their chemical or physical properties upon exposure to mechanical force, light, heat, or another stimulus or a combination of stimuli.^[1,2] This behavior can lead to materials with particular functions, for example self-healing.^[3] In a recent study,^[4] we investigated mechanoresponsive polymers containing ferrocene as a mechanophore. We, and in the meantime others,^[5] demonstrated the mechanical breaking of the sandwich complex, and a related release of metal ions in solution (Fig. 1).

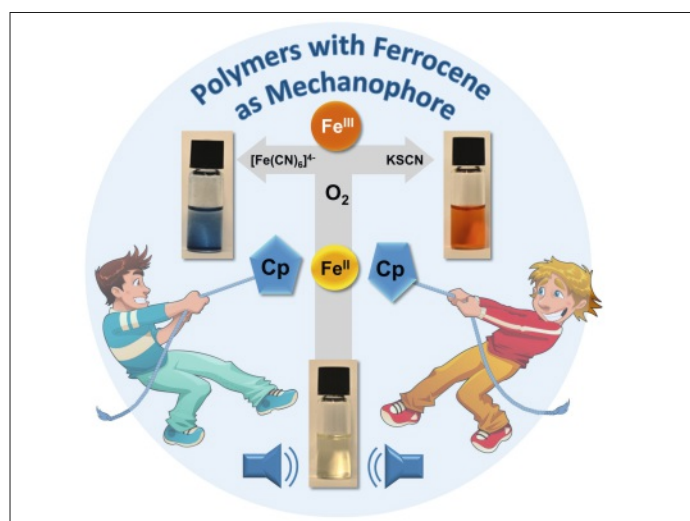


Fig. 1 Mechanoresponsive cleavage of ferrocene-containing polymers.

Although widely investigated in other contexts, ferrocene (Fc) had long remained unexplored as a mechanophore. Based on the low enthalpy of the heterolytic bond dissociation of Fc (40 kcal mol⁻¹), we surmised that this complex should be mechanically responsive and incorporated this motif as a chain-centered breakpoint in poly(methyl acrylate)s (Fc-PMAs) and in a statistically distributed manner in polyurethanes (FC-PU)s. We sonicated solutions of these polymers to trigger chain cleavage reactions and studied the molar mass as a function of sonication time of Fc-containing and Fc-free reference polymers (ref-PMA, Ref-PU) to prove preferential cleavage of the Fc motifs (Fig. 2a).

For both series the ultrasound-induced decrease of the molecular weight was analyzed using a recently developed kinetic model. Two competing scission events were discerned and related to the specific scission of the Fc motifs and also non-specific bond cleavage. The data show that the rate of Fc scission is at least 10 times higher than that of unspecific chain cleavage.

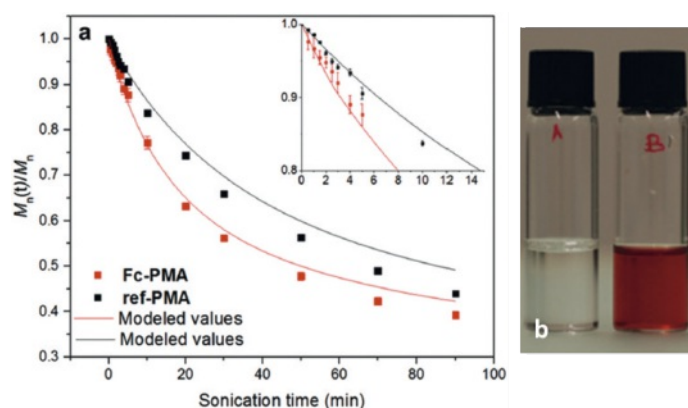


Fig. 2 a) Decrease of the normalized molecular weight ($M_n(t)/M_n$) of ref-PMA (black) and Fc-PMA (red) as a function of sonication time in THF. b) Pictures showing a Fc-PMA solution to which KSCN had been added before (left) and after (right) sonication. The red Fe-thiocyanate complex formed after sonication confirms the release of Fe ions upon sonication. Copyright (2018) Angewandte Chemie International Edition.

As further proof of the preferential cleavage of the Fc-containing polymers at the metal-organic site, the released and oxidized iron ions were detected by addition of KSCN, which generated the red $[\text{Fe}(\text{SCN})_n(\text{H}_2\text{O})_{6-n}]^{(3-n)+}$ complex (Fig. 2b) or reacted with $\text{K}_4[\text{Fe}(\text{CN})_6]$ to afford Prussian blue.

Our finding that ferrocene, and possibly other metallocenes, can be used as a mechanophore in polymers that allow the mechanically induced release of metal ions has recently been confirmed by Sha *et al.*, who conducted a similar study with several other polymers and corroborated that the Fe–Cp bond is the favorite cleavage site in ultrasound-induced degradation.^[5] The mechanistic studies are consistent with a heterolytic dissociation of ferrocene into Cp^- and $[\text{CpFe}]^+$.

Received: November 8, 2018

- M. A. C. Stuart, W. Huck, J. Genzer, M. Müller, C. Ober, M. Stamm, G. B. Sukhorukov, I. Szleifer, V. V. Tsukruk, M. Urban, F. Winnik, S. Zauscher, I. Luzinov, S. Minko, *Nature Mater.* **2010**, *9*, 101.
- K. M. Herbert, S. Schrettl, S. J. Rowan, C. Weder, *Macromolecules* **2017**, *50*, 8845.
- B. J. Blaiszik, S. L. B. Kramer, S. C. Olugebefola, J. S. Moore, N. R. Sottos, S. R. White, *Ann. Rev. Mater. Res.* **2010**, *40*, 179.
- M. Di Giannantonio, M. A. Ayer, E. V. Sesto, M. Lattuada, C. Weder, K. M. Fromm, *Angew. Chem. Int. Ed.* **2018**, *57*, 11445.
- Y. Sha, Y. Zhang, E. Xu, Z. Wang, T. Zhu, S. L. Craig, C. Tang, *ACS Macro Lett.* **2018**, *7*, 1174